

Porous Tantalum Cones for Large Metaphyseal Tibial Defects in Revision Total Knee Arthroplasty

A Minimum 2-Year Follow-up

William J. Long, MD, FRCSC, and Giles R. Scuderi, MD

Abstract: Sixteen cases of revision total knee arthroplasty requiring the use of porous tantalum tibial cones for 2 T2A, 3 T2B, 4 T3A, and 7 T3B tibial bone defects (Anderson Orthopaedic Research Institute classification) after 13 cases of aseptic loosening and 3 cases of staged reimplantation for infection were reviewed. At an average 31 months (24-38), no patients were lost to follow-up. There were 2 cases of recurrent sepsis requiring removal of a well-fixed cone. In the remaining 14 cases, the reconstructions were functioning well with no reoperations. Radiographs demonstrated reestablishment of the joint line, neutral mechanical axis (average, 5.4° of valgus), and signs of stable osteointegration into the cones. Good short-term results were achieved in complex revisions, with these new reconstructive tools. **Keywords:** porous tantalum cones, tibial bone loss, revision total knee arthroplasty.

© 2009 Elsevier Inc. All rights reserved.

Rates of revision total knee arthroplasty will continue to increase as more primary total joint arthroplasties are performed [1]. Complex revision total knee cases with significant tibial bone loss represent a challenging subset of patients. Reestablishment of a stable well-aligned and supported tibial base is necessary for successful reconstruction [2]. Historically, this has been achieved with impaction grafting [3,4], bulk allograft [5-10], tumor prostheses [11], custom components [12], or a combination of a large allograft combined with a stemmed revision component forming an allograft-prosthesis composite [13,14].

The porous metal tantalum provides a new tool for modular reconstruction in these cases. Important characteristics of tantalum include its negative charge and interconnective pores, which form a scaffolding and surface for osteoblast-mediated bone ingrowth [15-17]. The lower modulus of elasticity (3 MPa) and high (70%-80%) porosity allow for a more uniform stress transfer and the potential for diminished stress shielding. Basic science research has also demonstrated a lower bacterial adherence, and increased leukocyte activation, when compared to other orthopedic metal implant materials [18,19]. The uneven texture provides an initial scratch fit after insertion. Lastly, the modular nature of the cones allows the surgeon to choose a size and position that best fits the individual defect encountered [20].

Materials and Methods

Institutional review board approval was obtained for this retrospective review. All patients undergoing revision knee reconstruction for any reason, which required the use of a porous tantalum cone for tibial

From the Insall Scott Kelly® Institute of Orthopaedics and Sports Medicine, New York, New York.

Submitted March 24, 2008; accepted August 23, 2008.

One of the authors is a consultant for Zimmer Inc. Implex, Warsaw, IN, USA.

Reprint requests: William J. Long, MD, FRCSC, Attending Orthopaedic Surgeon, Insall Scott Kelly Institute for Orthopaedics and Sports Medicine, 210 East 64th Street, New York, NY 10065.

© 2009 Elsevier Inc. All rights reserved.

0883-5403/08/2407-0013\$36.00/0

doi:10.1016/j.arth.2008.08.011

reconstruction (Fig. 1), were included in this study. All cases were performed by the senior surgeon. These cases represent a consecutive series of patients as porous tantalum cones were used for all cases when massive tibial defects were encountered. In no cases were other techniques such as impaction or bulk allograft used as an alternative.

Our surgical technique has been previously described [21]. Briefly, reconstruction involved the removal of the failed prosthesis (Fig. 2) or bone cement spacer. Tibial lesions were debrided (Fig. 3A) and then graded according to the Anderson Orthopaedic Research Institute (AORI) classification system [22]. This classification system considers bone loss from the tibia and femur independently (T and F): small amounts of bone loss not compromising component stability are grade 1; damaged metaphyseal bone needing augmentation to maintain joint line are grade 2; significant bone loss compromising a major portion of the condyle or plateau that may involve detachment of the patellar tendon or collateral ligament are grade 3. Bone loss is then broken down further into 1 condyle/plateau (A) or 2 (B).

Trial tibial cones were inserted and minor adjustments were made to the depth and periphery of the defect to achieve appropriate seating of the cone (Fig. 3B). Tibial stem reaming was then performed, and the appropriately sized tibial trial was inserted in the correct rotation. Depth of insertion was judged using local landmarks including the tibial tubercle, fibular head, and remaining rim of bone. When a gap existed between the trial cone and the tibial plate, a medial or lateral wedge was inserted.

Femoral reconstruction proceeded as per standard reconstructive principles. The epicondyles were used for both rotation, as well as a rough estimate to joint line. Femoral component size was chosen to achieve a balanced flexion and extension gap while maintaining posterior condylar offset.



Fig. 1. Porous tantalum step cone before insertion.



Fig. 2. Failed primary knee with tibial osteolysis and subsidence.

The patellar component was then examined. A stable prosthesis with minimal wear was left in place. Loose components were removed and a decision was made regarding repeat cementing, porous tantalum augmentation, or patelloplasty.

After achieving a stable trial reconstruction, the trial polyethylene and tibial component were removed and the real porous tantalum augment was inserted. The cone was press fit into the remaining rim of bone in the same position as the trial. Gaps between the porous tantalum augment and the intact bony rim were filled with a mixture of morselized allograft bone, any autograft bone, and demineralized bone slurry (Fig. 3C). Once again, the trial tibial component and poly was inserted to ensure that the alignment, rotation, and joint line had not changed. The position of the trial components was marked and they were removed. Pulse lavage was then performed using antibiotic rinse.

When stable bony fit of the trial components was achieved, diaphyseal press-fit uncemented stems were used. In cases with thin cortices with wide canals where a good press-fit was not obtained, a cemented stem was chosen. When diaphyseal, metaphyseal offset existed, an offset stem was used. In all cases, the metaphyseal portion of the tibial component in the region of the augment was cemented. Antibiotic cement was used in all cases, 1.2 g of tobramycin per bag.

All patients were permitted to weight bear as tolerated postoperatively. The patient with an extensor mechanism allograft was placed in a stovepipe cast. All other patients were encouraged to mobilize through a full range of motion.

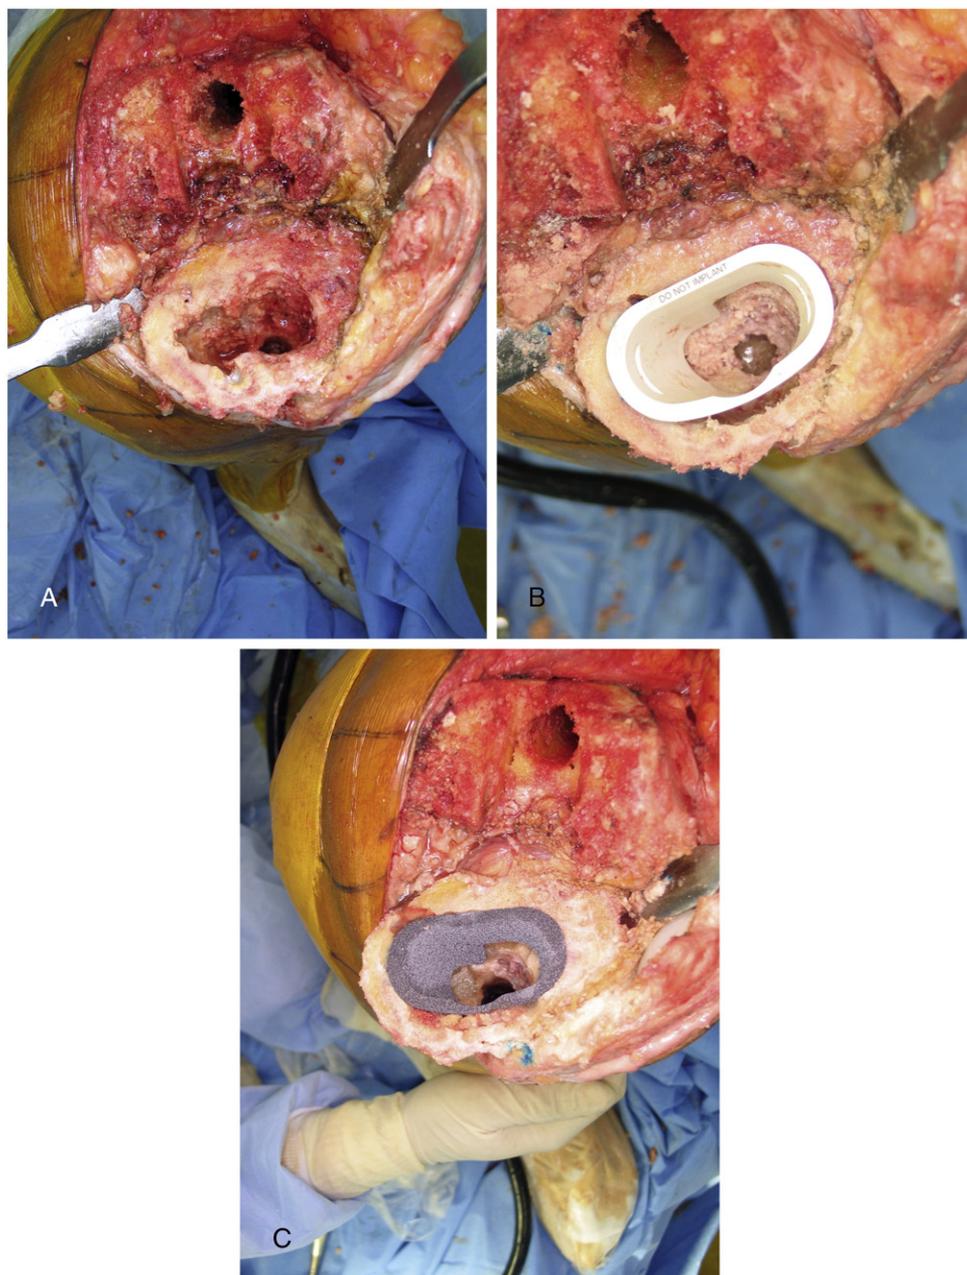


Fig. 3. A to C, Tibial defect, trial cone, and final cone positioned with moselized graft at the periphery.

Patients were seen at scheduled routine follow-ups at 3 weeks, 6 weeks, 6 months, and then yearly, for clinical and radiographic assessment.

Results

Demographics

Sixteen revision procedures were performed on 15 patients. Average patient age at surgery was 66.1 years (range, 48-83 years). There were 8 females (1 case bilateral) and 7 males. Seven cases involved left knees and 9 right knees. The diagnosis was aseptic

loosening in 13 cases and staged reimplantation after infection in 3 cases.

Surgical Data

Approaches included 15 medial parapatellar and 1 midline (associated with the extensor allograft). A quadriceps snip was required in 5 cases, and in 2 of those, a tibial tubercle osteotomy was also needed for exposure. Metal wires were used for tubercle osteotomy fixation (3 in 1 case and 2 in the other). All wires were placed distal to the cones, and bone healing was achieved in both cases. Ten medial

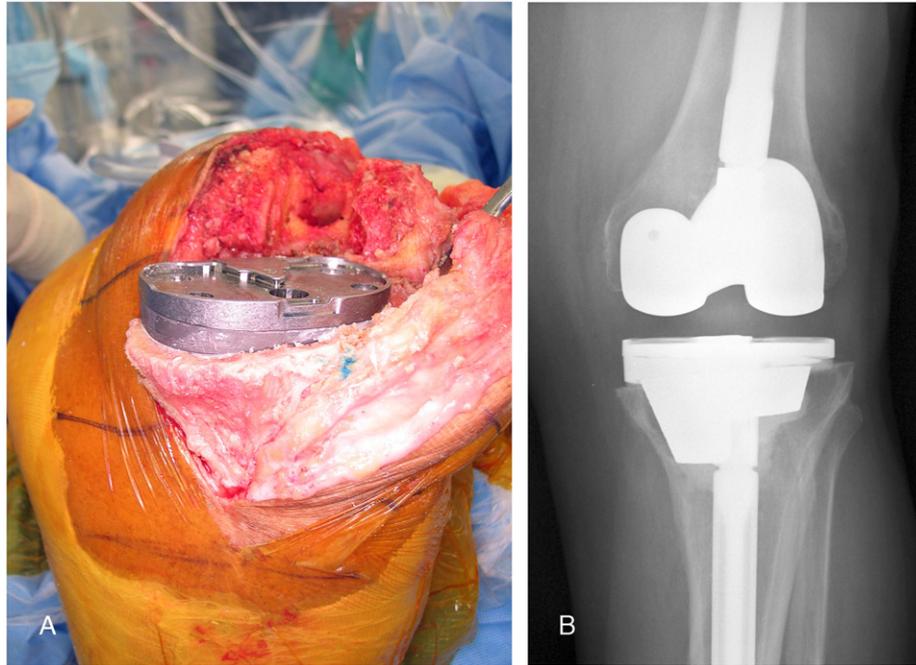


Fig. 4. A and B, Completed tibial reconstruction with hybrid cement technique and a wedge augment on top of the stable base created by the cone.

releases were required for soft tissue balancing and 4 lateral patellar releases were performed to achieve central patellar tracking.

On the femoral side, posterior and/or distal porous metal augments were used in all cases. Two femoral cones were needed to address femoral bone loss, both F3B (AORI Classification). Patellar management involved 8 retained well-fixed originals, 1 all-poly cemented revision, 4 porous tantalum augments and cemented poly patellar components, 2 patelloplasty, and 1 extensor mechanism allograft (patella unresurfaced). The extensor mechanism allograft was performed as per the technique of Burnett et al [23].

Tibial defects were classified according to the AORI system as 2 T2A, 3 T2B, 4T3A, and 7 T3B tibial bone defects. In all of these cases, a cone was required to reestablish a stable proximal tibial platform for knee reconstruction. Of the 16 cones used, 5 were stepped (30/15 mm). Two large and 3 medium step cones were inserted. Four of the steps were thicker medially and 1 laterally. The 11 remaining cones were nonstepped and consisted of 2 extra small (48 × 15), 3 small (52 × 15), 4 medium (one 59 × 15 mm, three 59 × 30 mm), and 2 large (one 67 × 15, one 67 × 30). There were no fractures or complications related to the insertion and impaction of the cones.

Fixation involved hybrid fixation, with proximal cementation through the region of the cone in 12 cases and a cemented stem in 4 cases. Cemented

tibial rods were 75 to 100 mm in length, and diaphyseal press-fit uncemented stems were from 75 to 200 mm in length. Four rods were offset.

Tibial augments were required in 8 cases on top of the porous tantalum cone (Fig. 4A and B). Seven medial and 1 lateral wedge were used. In all cases, a constrained-condylar polyethylene tibial insert was used. Poly thicknesses ranged from 10 to 23 mm. In no cases was a hinged prosthesis required to achieve stability.

Clinical Outcomes

Two cases of recurrent infection occurred. In the first case, the reconstruction was performed in conjunction with an extensor mechanism allograft for staged revision of a failed revision total knee arthroplasty with extensor deficit. Resection was performed at 8 months postoperatively. At that time, the tibial cone was noted to be well ingrown with bone and required significant work with a burr and osteotome along the interface to remove the cone.

The second case was also a recurrent infection and occurred 3 months postoperatively. Resection was performed at an outside institution. The surgeon's notes report stable bony ingrowth of the tibial cone at the time of resection.

The remaining 14 cases were functioning well and average 31 months follow-up (24-38 months). All patients achieved full extension on clinical

examination, and average range of motion was 109° (range, 90°-120°). Knees were stable to varus-valgus stress in extension and to anteroposterior stress in flexion. Patella tracked well in all cases. Good quad strength was noted with no extensor lag on straight leg raise. No significant pain was noted in 13 patients. One patient with inflammatory arthritis complained of mild aching and had a mild effusion. Septic workup, including aspiration, was negative for infection. Of 14 patients, 13 walked without aids. One patient, aged 86 years, is now living in a nursing home, has moderate dementia, and uses a walker for ambulation, but not because of the operated knee. There were no cases of aseptic loosening. No revisions or reoperations were performed, or planned in the 13 patients (14).

Radiographic Outcomes

Serial x-rays were examined preoperatively, postoperatively, and at each subsequent visit. Review of the 14 nonrevised cases revealed signs of stable bony ingrowth at the bone-trabecular metal interface, and streaming trabeculations into the trabecular surface. Average tibiofemoral alignment was 5.4° of valgus (range, 4°-7°). No cases of progressive osteolysis, loosening, or subsidence were noted.

In the 2 cases with a tibial tubercle osteotomy for exposure, there was stable bone healing both distal

to and at the level of the cone. No wires required removal (Fig. 5).

Discussion

Large tibial bone defects present a challenging reconstructive problem. Traditionally, lesions have been treated with bone in the form of bulk allograft or impaction grafting [3-10], modular tumor or custom components [11,12], or allograft-prosthesis composites [13,14]. All of these techniques have been shown to be durable in midterm outcomes, but concerns exist for a number of reasons, including disease transmission; resorption, fracture, or immune reaction to allograft; the cost of custom prostheses, and the inability to modify the construct intraoperatively; and the overall technical challenge of applying these techniques.

Porous tantalum augments provide surgeons with a powerful tool for addressing these concerns. When compared to bone, there is no risk of disease transmission, fracture, or resorption. In contrast to custom prostheses, cones are used in a modular nonlinked fashion, can be inserted at multiple angles and positions, can be used with any revision system, and come in a number of sizes, to address the specific dimensions of the lesion encountered. Biomechanical studies have shown a modulus of elasticity closer to that of bone and an interconnective porous nature that allows bony ingrowth suggesting the possibility for more stable long-term fixation [16,17]. Recent animal studies have also shown promise in achieving patellar tendon attachment to porous tantalum structures [24].

Multiple studies examining the use of porous tantalum acetabular cups in hip reconstruction have been published [25-27] and presented [28]. Porous acetabular augments have been designed and used as an alternative to allograft bone reconstruction for large acetabular defects [29,30]. They have all shown very promising early clinical results, although long-term data do not yet exist.

Clinical results at a minimum 2 years with 15 porous tantalum cones used in revision total knee arthroplasty were recently published [31]. No cases of aseptic loosening or migration were noted at an average 34 months. Evidence of osteointegration was observed on follow-up radiographs.

This study is the second that we are aware of to demonstrate good early outcomes with porous tantalum cones for large tibial defects. Even in the 2 cases where components were removed because of recurrent infection, the porous cones were found to be well fixed with stable bony



Fig. 5. A lateral radiograph demonstrating a healed tibial tubercle osteotomy.

ingrowth. We do not believe that the high rate of reinfection (2/3) in this complex subset of patients is related to the use of porous tantalum cones. In fact, we believe that the porous cones are a better alternative than placing large amounts of dead bone or large metal augments into the defect. Basic science research has demonstrated lower bacterial adherence and increased leukocyte activation on porous tantalum surfaces when compared with other reconstructive materials [18,19].

The remaining 14 knees were functioning well with radiographic evidence of osteointegration of the cones. Short-term results with the use of porous tantalum cones for tibial bone loss in revision total knee arthroplasty show promising results. In particular, the potential for long-term biologic fixation distinguishes this technique from other options. This is an early retrospective study, and certainly longer-term follow-up will be important in determining the durability of these new reconstructive tools.

Acknowledgment

The authors would like to acknowledge the assistance of Dr Henrik Bo Pedersen in manuscript and figure preparation.

References

- Iorio R, Robb WJ, Healy WL, et al. Orthopaedic surgeon workforce and volume assessment for total hip and knee replacement in the United States: preparing for an epidemic. *J Bone Joint Surg Am* 2008;90:1598.
- Haas SB, Insall JN, Montgomery III W, et al. Revision total knee arthroplasty with use of modular components with stems inserted without cement. *J Bone Joint Surg Am* 1995;77:1700.
- Bradley GW. Revision total knee arthroplasty by impaction bone grafting. *Clin Orthop Relat Res* 2000;113.
- Lotke PA, Carolan GF, Puri N. Impaction grafting for bone defects in revision total knee arthroplasty. *Clin Orthop Relat Res* 2006;446:99.
- Engh GA, Herzworm PJ, Parks NL. Treatment of major defects of bone with bulk allografts and stemmed components during total knee arthroplasty. *J Bone Joint Surg Am* 1997;79:1030.
- Tsahakis PJ, Beaver WB, Brick GW. Technique and results of allograft reconstruction in revision total knee arthroplasty. *Clin Orthop Relat Res* 1994;86.
- Ghazavi MT, Stockley I, Yee G, et al. Reconstruction of massive bone defects with allograft in revision total knee arthroplasty. *J Bone Joint Surg Am* 1997;79:17.
- Clatworthy MG, Ballance J, Brick GW, et al. The use of structural allograft for uncontained defects in revision total knee arthroplasty. A minimum five-year review. *J Bone Joint Surg Am* 2001;83-A:404.
- Backstein D, Safir O, Gross A. Management of bone loss: structural grafts in revision total knee arthroplasty. *Clin Orthop Relat Res* 2006;446:104.
- Engh GA, Ammeen DJ. Use of structural allograft in revision total knee arthroplasty in knees with severe tibial bone loss. *J Bone Joint Surg Am* 2007;89:2640.
- Springer BD, Hanssen AD, Sim FH, et al. The kinematic rotating hinge prosthesis for complex knee arthroplasty. *Clin Orthop Relat Res* 2001;283.
- Kress KJ, Scuderi GR, Windsor RE, et al. Treatment of nonunions about the knee utilizing custom total knee arthroplasty with press-fit intramedullary stems. *J Arthroplasty* 1993;8:49.
- Harris AI, Poddar S, Gitelis S, et al. Arthroplasty with a composite of an allograft and a prosthesis for knees with severe deficiency of bone. *J Bone Joint Surg Am* 1995;77:373.
- Dennis DA. The structural allograft composite in revision total knee arthroplasty. *J Arthroplasty* 2002;17(4 Suppl 1):90.
- Bobyn JD, Stackpool GJ, Hacking SA, et al. Characteristics of bone ingrowth and interface mechanics of a new porous tantalum biomaterial. *J Bone Joint Surg Br* 1999;81:907.
- Findlay DM, Welldon K, Atkins GJ, et al. The proliferation and phenotypic expression of human osteoblasts on tantalum metal. *Biomaterials* 2004;25:2215.
- Welldon KJ, Atkins GJ, Howie DW, et al. Primary human osteoblasts grow into porous tantalum and maintain an osteoblastic phenotype. *J Biomed Mater Res A* 2008;84:691.
- Schildhauer TA, Robie B, Muhr G, et al. Bacterial adherence to tantalum versus commonly used orthopedic metallic implant materials. *J Orthop Trauma* 2006;20:476.
- Schildhauer TA, Peter E, Muhr G, et al. Activation of human leukocytes on tantalum trabecular metal in comparison to commonly used orthopedic metal implant materials. *J Biomed Mater Res A* 2008.
- Bobyn JD, Poggie RA, Krygier JJ, et al. Clinical validation of a structural porous tantalum biomaterial for adult reconstruction. *J Bone Joint Surg Am* 2004;86-A(Suppl 2):123.
- Radnay CS, Scuderi GR. Management of bone loss: augments, cones, offset stems. *Clin Orthop Relat Res* 2006;446:83.
- Engh GA, Ammeen DJ. Classification and preoperative radiographic evaluation: knee. *Orthop Clin North Am* 1998;29:205.
- Burnett RS, Berger RA, Della Valle CJ, et al. Extensor mechanism allograft reconstruction after total knee arthroplasty. *J Bone Joint Surg Am* 2005;87(Suppl 1 (Pt 2)):175.
- Itälä A, Heijink A, Leerapun T, et al. Successful canine patellar tendon reattachment to porous tantalum. *Clin Orthop Relat Res* 2007;463:202.

25. Unger AS, Lewis RJ, Gruen T. Evaluation of a porous tantalum uncemented acetabular cup in revision total hip arthroplasty clinical and radiological results of 60 hips. *J Arthroplasty* 2005;20:1002.
26. Komarasamy B, Vadivelu R, Bruce A, et al. Clinical and radiological outcome following total hip arthroplasty with an uncemented trabecular metal monoblock acetabular cup. *Acta Orthop Belg* 2006;72:320.
27. Rose PS, Halasy M, Trousdale RT, et al. Preliminary results of tantalum acetabular components for THA after pelvic radiation. *Clin Orthop Relat Res* 2006;453:195.
28. Long WJ, Noiseux NO, Mabry TM, Hanssen AD, Lewallen DG. Uncemented porous tantalum acetabular components: early follow-up and failures in 1212 cases. Podium presentation 016, AAOS San Diego 2007.
29. Nehme A, Lewallen DG, Hanssen AD. Modular porous metal augments for treatment of severe acetabular bone loss during revision hip arthroplasty. *Clin Orthop Relat Res* 2004;201.
30. Sporer SM, Paprosky WG. The use of a trabecular metal acetabular component and trabecular metal augment for severe acetabular defects. *J Arthroplasty* 2006;21(6 Suppl 2):83.
31. Meneghini RM, Lewallen DG, Hanssen AD. Use of porous tantalum metaphyseal cones for severe tibial bone loss during revision total knee replacement. *J Bone Joint Surg Am* 2008;90:78.